

Influence of Curing Temperature on Shear Strength and Compressibility of Swelling Soil Stabilized with Hydrated Lime

Nihad Bahaaldeen Salih* and Tavga Aram Abdalla**

**Department of Water Resources Engineering, College of Engineering, University of Sulaimani, Northern Iraq*

***Department of Civil Engineering, College of Engineering, University of Sulaimani, Northern Iraq*

**Corresponding Author, E-mail: tavga.aram@gmail.com or tavga.abdalla@univsul.edu.iq*

Submitted : 07-04-2021

Revised : 23-09-2021

Accepted : 02-10-2021

ABSTRACT

The exposed cohesive soils to temperature can face considerable physical and mechanical characteristic changes. Therefore, understanding the environmental events' influence on the soil geotechnical properties is essential, which is significant in rainy and cold places such as Sulaimani City, northern Iraq. This experimental study examines the temperature changes (10° C, and 50° C) impact on the durability of stabilized cohesive soil using 0%, 5%, 10%, and 15% hydrated lime added as a replacement for the soil dry mass. Consistency, unconfined compression, and compressibility characteristics were evaluated. Under the applied circumstances, a decrease was noticed in the magnitudes of liquid limit and plasticity index, while the plastic limit generally increased within the hydrated-lime percent increase. The study yielded an appreciable improvement of the cohesive soil's strength and compressibility properties with time progress, especially after the stabilization process is achieved.

Keywords: Cohesive Soil; Hydrated Lime; Temperature; Consistency; Strength; Compressibility.

INTRODUCTION

In the last two decades, the impact of heating and cooling on clay soils as a technique of soil stabilization has been of considerable interest and has had a major influence on many applications in engineering projects. Soil compressibility and permeability can be influenced by heating and cooling conditions (Qi et al., 2008). Lime has been used to enhance fine soil characteristics for a considerable time. Lime is useful in causing a modification in soil durability, shear strength, and plasticity (Al-Rawas et al., 2005; Guney et al., 2007; Dash and Hussain, 2012; Karkush and Abdulkareem, 2019; Abdalla and Salih, 2020). Physical and mechanical properties of expansive soil can be improved by using industrial by-products such as lime, fly ash, Microbial Calcite, silica fume, and natural pozzolana (Thyagaraj et al., 2012; Karkush et al., 2018; Noolu et al., 2018; Gadouri et al., 2019 AL-Ani et al., 2021). However, clayey soils plasticity instantaneously change (more or less) by using lime (Bagherpour and Choobbasti, 2003; Goswami and Singh, 2005; Ansary et al., 2006; Kavak and Akyarli, 2007; Manasseh and Olufemi, 2008). Then, several investigators (George et al. 1992; Rao and Shivananda 2005) concluded that there are still unclear problems with regard to the soil-lime acceleration relationship after thermal curing. Hence, significant improvements in soil's elasticity modulus and strength were achieved by George et al. (1992); a 50°C curing temperature was checked which was performed to obtain any potential benefits of high temperature on the soil-lime mixture. After that, compression (Cc) and swelling (Cr) indices were found to be negligible with temperature variations (Campanella and Mitchell, 1968). However, Cs (Abuel-Naga et al., 2007) and Cc (Tsutsumi and Tanaka, 2012) were changed with temperature. So, the Cv rate was increased as the temperature degree increased (Abuel-Naga et al., 2005). The variability of

permeability with temperature causes that, as temperature rises, permeability rises (Abuel-Naga et al., 2005; Cui et al., 2009). High temperatures ($5^{\circ}\text{C} - 70^{\circ}\text{C}$) resulted in slight variation in compression and swelling indices (Jarad, 2016), due to the dependency of these indices more on the applied pressure than temperature changes. The study's aim is to investigate the influences of curing temperature on the geotechnical characteristics of stabilized CL soil by hydrated lime. Potentially, the implementation of curing temperature variations on cohesive soil stabilized by hydrated lime modifies the soil behavior for various states of loading and saturation.

STUDY METHODOLOGY

MATERIAL USED

EXPANSIVE SOIL SAMPLE

An intact soil sample categorized as low plasticity clay (CL) soil (USCS) was selected (see Figure 1, and Table 1), namely Barika soil, Sulaimani Governorate, northern Iraq (Latitude = 35.393755 and Attitude = 45.595097). Some investigators (Rashed et al., 2017; Dong et al., 2019; Asad et al., 2019; Karkush and Yassin, 2020) recently used the soil site, which features clayey soils. The soil sample was collected from 1.0 to 2.0 meters depth from the natural ground level.

USED HYDRATED-LIME

The selected hydrated lime (see Table 2) is locally available and specifically used in building projects. It is obtained from Karbala Lime Factory, southern east of Iraq.

Table 1. The used cohesive sample engineering characteristics.

Property	Value
Natural Moisture Content (%)	18.68
Color	Light Brown
Silt + Clay (%)	70
Liquid limit, L.L. (%)	44.63
Plastic limit, P.L. (%)	19.46
Plasticity index, P.I.	25.17
Specify gravity (Gs)	2.67
M.D.D. (gm/cm ³)	1.57
O.M.C. (%)	27.25
Soil Type (USCS)	CL

Table 2. Some engineering characteristics for the used hydrated-lime.

Mineral Type	(%)
CaO	56.1
MgO	0.13
Fe ₂ O ₃	0.12
Al ₂ O ₃	0.72
SiO ₂	1.38
SO ₃	0.21
L.O.I	40.6
Physical Properties	
Passing sieve No.200 (%)	98
Surface Area (m ² /kg)	398
Specific Gravity (G _s)	2.78

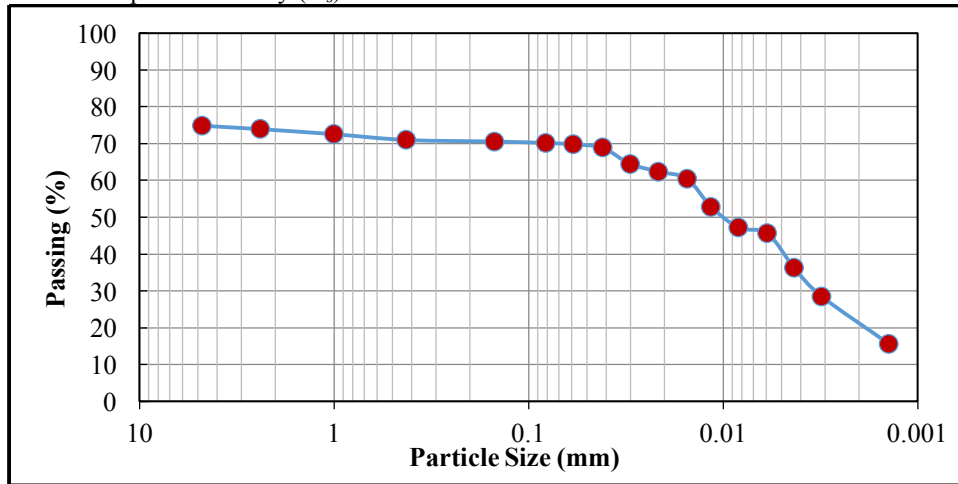


Figure 1. Drawn curve of cohesive soil sample particle-size.

METHOD OF TESTING

ATTERBERG LIMITS TESTS

Liquid and plastic limits and plasticity index were determined by using ASTM D4318 (2000). Plasticity index (PI) Variations were then studied before and after using hydrated lime (0%, 5%, 10%, and 15%). Therefore, the air-dried soil sample was sieved (No. 40), and the required hydrated lime percentages were prepared and mixed thoroughly with the soil sample. De-ionized water was used for the soil-lime mixture preparation, which was left in order to mature for 24 hours in an airtight container.

MECHANICAL INDICES

The unconfined compressive strength (UCS) samples (38 mm diameter, and 83 mm height) were tested (ASTM D2166, 2000) by using a 0.5 mm/min extension rate, which continued until the sample failure. In addition, the 1-D consolidation test (50 mm diameter, and 20 mm thickness) was conducted according to ASTM D 2435 (2011). For assessing the influence of curing temperature on the strength and compressibility components, the prepared samples were arranged at 25°C-27°C and kept in sealed containers, then cured for various durations (0, 7, 14, & 28 days). The curing process was performed for 10° C and 50° C.

SAMPLES PREPARATION AND TESTING PROCEDURCE

- Preparing a clean steel mold (38 mm diameter and 83 mm height) to prepare the untreated and treated soil sample for UCS determination that was experimented at an axial strain of 0.5 mm/min.
- Utilization of a ring of 50 mm thickness and 20 mm diameter for the conduction of a 1-D consolidation test for the intact and treated soil samples.
- For the treated samples, the hydrated lime is added at a percentage of 0%, 5%, 10%, and 15% as a replacement for the dry mass of the intact soil sample.
- To determine the effect of curing temperature on the strength and compressibility parameters of the treated soil, three samples were prepared for each added percent of hydrated lime at room temperature (25°C-27°C).
- The test samples were cured at temperatures of 10°C, and 50°C by leaving them in sealed containers for curing (0, 7, 14, and 28 days) before testing.
- For each hydrated lime content and curing period, three identical samples were tested and the average value was considered.
- Finally, all the prepared soil samples after being subjected to the curing temperatures were tested for determination of the UCS and 1-D consolidation parameters.

OBTAINED RESULTS AND THEIR DISCUSSIONS

ATTERBERG LIMITS

Each relationship of the presented Atterberg limits of the treated samples (see Figure 2) showed a different response to the carried-out soil treatment. It is clear that, with hydrated-lime percent increase (0% to 15%), liquid limit (LL) and PI values were reduced (-19.34% and -88.04% respectively). However, the plastic limit (PL) value tends to rise, 69.52% variation was obtained. Overall, an increase in the hydrated-lime content has resulted in plasticity characteristics reduction, similar to the findings of Ansary et al. (2006); Amu et al. (2011); Khattab and Aljobouri (2011); Dash and Hussain (2012); Gharib et al. (2012); Mohammed and Elsharief (2015). The occurrence of cation exchange as a consequence of some ions' interchange with hydrated lime may cause an instant variation in the material workability, which can happen inside the clay structure. Therefore, the PL increased and the PI decreased (Thyagaraj and Zodinsanga, 2014; Jha and Sivapullaiah, 2015). The plasticity changes take place more over time, due to the influence of pozzolan reactions that start to affect so that PI continues to decrease. This plasticity reduction gives a further brittle texture for the soil-lime mixtures, rendering the soil more vulnerable to field equipment movement and manipulation.

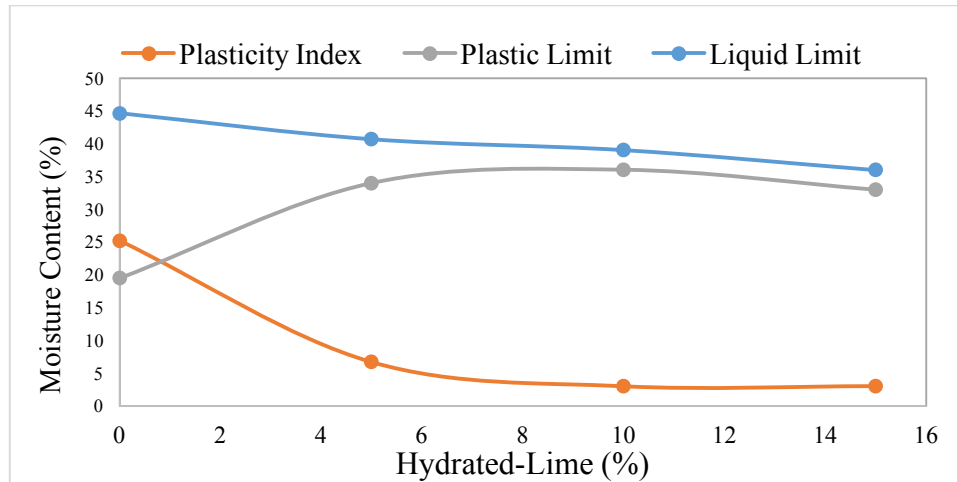


Figure 2. Variation of Atterberg limits and plasticity index with hydrated-lime percent increase.

UNCONFINED COMPRESSION TEST

At elevated curing temperature (hydrated-lime percent increase), sample strength significantly rises (Figures 3 and 4). The gained strength due to the hydrated-lime content increase is marginal for the cured samples by 10°C. The addition of hydrated lime (0 % to 15%) caused the UCS to be increased (269.41 kPa to 616.6 kPa) when cured at 10 ° C for 28 days. However, a significant improvement in the strength of the samples (386.21 kPa to 2514.98 kPa) was obtained within 28 days of curing at 50° C, which happened when the hydrated lime content increased from 5% to 15%.

Higher strength was achieved as a comparison between applications of 50°C and 10°C. This shows that not only does the hydrated-lime content cause modification, but a major role also can be achieved in accelerating the mixture of hydrated-lime and soil reactions. The results clearly show that curing time and temperature for 0% hydrated-lime percent treated samples are not very successful in gaining strength. In comparison, at 15% hydrated-lime content cured by 50°C, the highest strength rate increase was obtained. Importantly, it is clear that the 7-day curing period is essential to gain higher strength regardless of the hydrated-lime content and temperature degree for curing. In addition, the strength gain rate decreased gradually due to the curing period increased. This depends on the hydrated-lime quality and curing temperature degree. Similarly, UCS modification for stabilized soils by lime was obtained by (Osinubi and Nwaiwu (2006); and Amadi and Okeiyi (2017).

The cation interchange, which is a physicochemical phenomenon that happens between clay particles and hydrated lime in addition to the process of flocculation-agglomeration, can be because of the shear strength enhancement of the stabilized soil by hydrated lime. Instant changes in the stabilized soil properties will take place quickly due to the mentioned actions. Moreover, among silica, alumina, and calcium ions, pozzolanic reactions after that will happen for the samples of clay minerals. The obtained results are similar to the results of Alzubaidi and Lafta (2013); Zhao et al (2014); and Jha and Sivapullaiah (2015) for the production of cement products for strength increase.

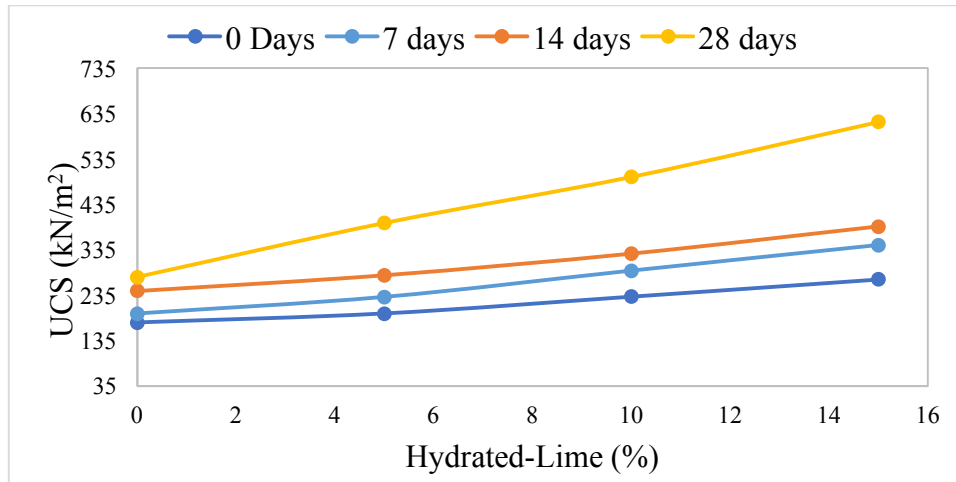


Figure 3. Hydrated-lime and curing period (at 10° C) impacts on unconfined compressive strength.

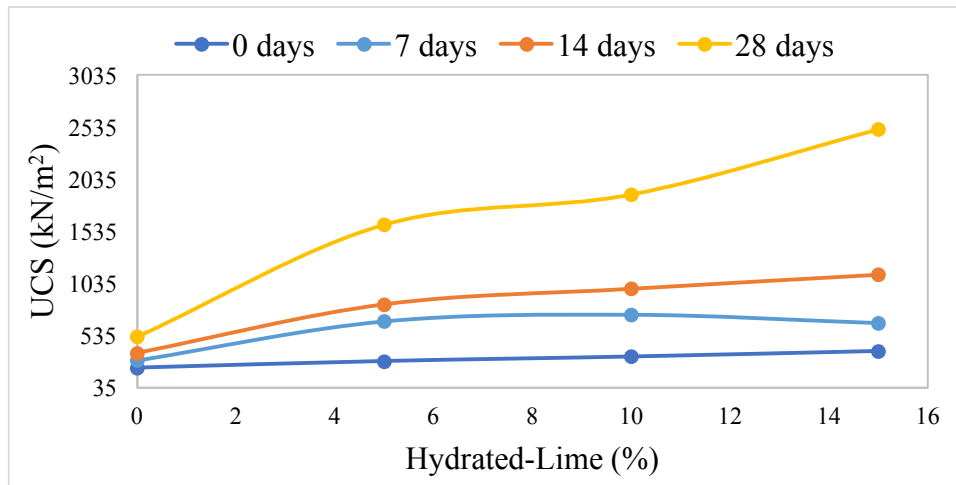


Figure 4. Hydrated-lime and curing period impacts (at 50° C) on unconfined compressive strength.

ONE-DIMENSIONAL CONSOLIDATION

The compressibility characteristics of CL soil samples with various hydrated-lime percent and different curing temperatures at 10°C and 50°C after 0, 7, 14, and 28 days have been studied. The compression index (C_c) and swelling index (C_r) were decreased due to curing temperature increase (Figures 5 and 6). The addition of 15% hydrated-lime cured for 28 days at 10 ° C resulted in C_c and C_r decrease from 0.1204 to 0.0294 and 0.017 to 0.005 respectively. However, the improvement in compressibility characteristics can be noticed after the samples are cured at 50°C. C_c and C_r changes (see Figures 7 and 8) are 0.1042 - 0.0112 and 0.012847 - 0.00567 respectively due to 15% hydrated lime and 28 days of curing.

Lower compressibility was achieved for stabilized soil samples by hydrated-lime cured at 50°C compared to similar stabilized samples cured at 10°C. This achieved outcome shows that the hydrated lime is not only the factor that has modified the compressibility parameters, the curing temperature and time also caused notable modifications in the values of C_c and C_r . The thermal curing process therefore importantly caused reductions in the stabilized samples C_c and C_r . Similarly, the role of temperature in decreasing soil's compressibility properties was proven in some studies such as Marques et al. (2004); Tang et al. (2007); Tsutsumi and Tanaka (2012).

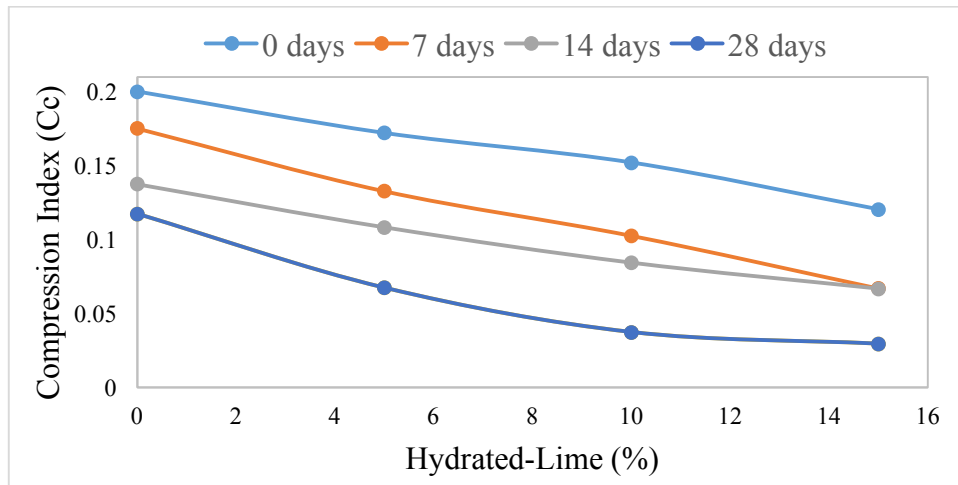


Figure 5. Hydrated-lime and curing time (at 10° C) impacts on compression index.

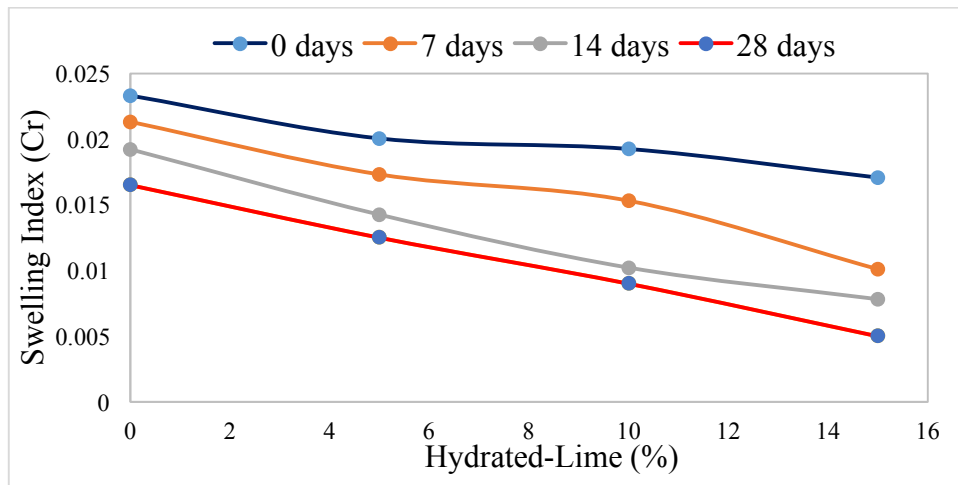


Figure 6. Hydrated-lime and curing period (at 10° C) impacts on swelling index.

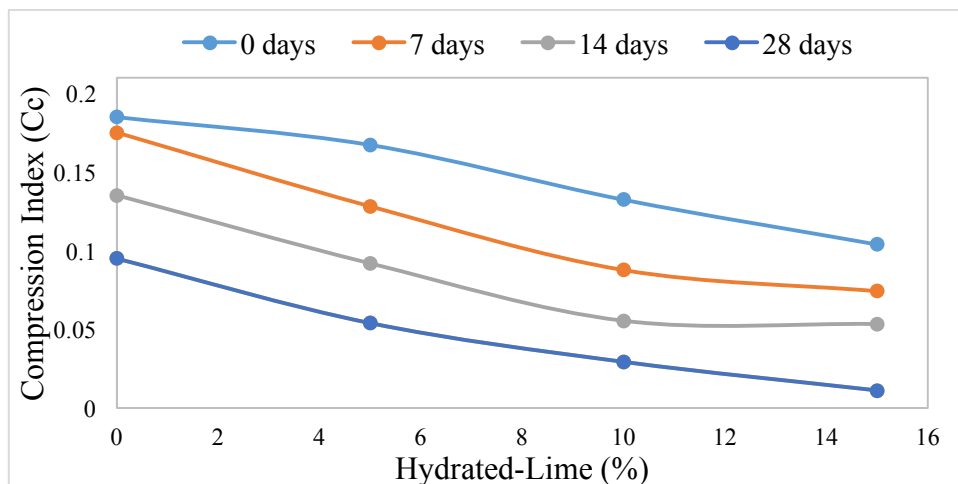


Figure 7. Hydrated-lime and curing period (at 50° C) impacts on compression index.

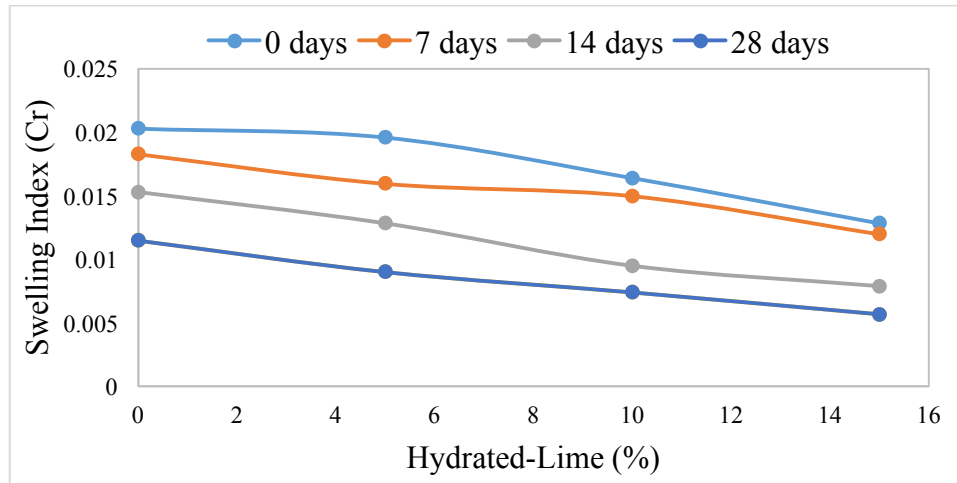


Figure 8. Hydrated-lime and curing time (at 50° C) on swelling index.

CONCLUSIONS

Considering the achieved results from the extensive experimental testing program, the outcomes yielded in the following conclusions:

- Utilization of hydrated lime with curing temperature increases and importantly decreases consistency parameters, plasticity index, and liquid limit.
- Hydrated lime significantly increased unconfined compressive strength, which is very susceptible to curing temperature; the highest strength was gained after 28 days of curing at 50° C.
- The addition of hydrated lime resulted in an appreciable effect on decreasing C_c and C_r at different curing temperatures and times, especially due to 15% hydrated lime, and 50° C for 28 days of curing time.

REFERENCES

- Abdalla, T. A. and Salih, N. B. 2020.** Hydrated Lime Effects on Geotechnical Properties of Clayey Soil. *Journal of Engineering* 26 (11):150-169.
- Abuel-Naga, H. M., Bergado, D. T., Bouazza, A., Ramana, G. V. 2007.** Volume change behavior of saturated clays under drained heating conditions: experimental results and constitutive modeling. *Canadian Geotechnical Journal* 44: 942-956.
- Abuel-Naga, H. M., Bergado, D. T., Soralump, S., Rujivipat, P.2005.** Thermal consolidation of soft Bangkok clay. *Lowland Technology International* 7: 13-21.
- AL-Ani, S.M., Karkush, M.O., Zhussupbekov, A. and Al-Hity, A.A. 2021.** Influence of Magnetized Water on the Geotechnical Properties of Expansive Soil. In *Modern Applications of Geotechnical Engineering and Construction* (pp. 39-50). Springer, Singapore.
- Al-Rawas, A. A., Hago, A. W., and Al-Sarmi H. 2005.** Effect of Lime, Cement and Sarooj (Artificial Pozzolan) on the Swelling Potential of an Expansive Soil from Oman. *Build Environ* 40: 681–687.
- Alzubaidi, R., Lafta, S. 2013.** Effect of strain rate on the strength characteristics of soil–lime mixture. *Geotech Geol Eng.*
- Amadi, A. A. and Okeiyi, A.2017.** Use of quick and hydrated lime in stabilization of lateritic soil: comparative analysis of laboratory data. *Geo-Engineering* 8 (3): 1-13.
- Amu, O. O., Bamisaye, O. F., and Komolafe, I. A. 2011.** The suitability and lime stabilization requirement of some lateritic soil Samples as pavement. *International Journal of Pure and Applied Sciences and Technology* 2 (1): 29-46.
- Ansary, M.A., Noor, M.A., and Islam, M. 2006.** Effect of fly ash stabilization on geotechnical properties of Chittagong coastal soil.” *Soil Stress-Strain Behavior: Measurements, Modeling and Analysis Geotechnical Symposium in Roma, March 16 & 17: 443–454.*
- Asad, A., Hussain, A., Farhan, A., Bhatti, A. A., and Munir, M. 2019.** Influence of lime on low plastic clay soil used as subgrade. *J. Mech. Cont. & Math. Sci* 14 (1): 69-77.
- ASTM, D2166.2000.** Standard Test Methods for Unconfined Compressive Strength of Cohesive Soil. ASTM International, West Conshohocken, PA, USA.
- ASTM, D2435 .2011.** Standard Test Methods for One - Dimensional Consolidation Properties of Soils Using Incremental Loading. ASTM International, West Conshohocken, PA, USA.
- ASTM, D4318 .2000.** Standard Test Methods for Liquid Limit, Plastic Limit, and Plasticity Index of Soils. ASTM International, West Conshohocken, PA, USA.
- Bagherpour, I. and Choobbasti, A. J. 2003.** Stabilization of fine grained soils by adding micro Silica and Lime or Micro Silica and Cement. *Electron J. Geotech Eng* 8: 1–10.
- Campanella, R. G., Mitchell, J. K. 1968.** Influence of temperature variations on soil behavior. *ASCE* 94: 709-734.
- Cui, Y., Le, T. T., Tang, A. M., Delage, P., and Li, X. L. 2009.** Investigating the Time Dependent Behavior of Boom Clay under Thermo-Mechanical Loading. *Géotechnique* 59:319-329.

- Dash, S. K. and Hussain, M. 2012.** Lime stabilization of soils. *Journal of Materials in Civil Engineering, ASCE* 24 (6):707-714.
- Dong, J. G., Xu, G. Y., Lv, H. B., & Yang, J. Y. 2019.** Development of instrument for wetting-drying cycles of expansive soil under simulated loads and experimental research. *Journal of Engineering Research* 7(3): 1-12
- Gadouri, H., Harichane, K., & Ghrici, M. 2019.** Effect of the interaction between calcium sulphate and mineral additives on shear strength parameters of clayey soils. *Journal of Engineering Research* 7(2): 66-88.
- George, S. Z., Ponniah, D. A., and Little, J. A. 1992.** Effect of temperature on lime-soil stabilization. *Construction and Building Materials* 6 (4):247-252.
- Gharib, M., Saba, H. and Barazesh, A. 2012.** Experimental Investigation of Impact of Adding Lime on Atterberg Limits in Golestan Province Soils. *Journal of Applied and Basic Sciences, ECISI* 3 (4):796 – 800.
- Goswami, R. K. and Singh, B. 2005.** Influence of fly ash and lime on plasticity characteristics of residual lateritic soil. *Ground Improvement* 9: 175–182.
- Guney, Y., Sari, D., Cetin, M., and Tuncan, M. 2007.** Impact of Cyclic Wetting-Drying on Swelling Behaviour of Lime-Stabilized Soil. *Build Environ* 42: 681–688.
- Jarad .2016.** Temperature impact on the consolidation and creep behaviour of compacted clayey soils. PhD thesis. *Mechanics of materials [physics. class-ph]*. Université de Lorraine, France.
- Karkush, M.O. and Abdulkareem, M.S. 2019.** Deep remediation and improvement of soil contaminated with residues oil using lime piles. *International Journal of Environmental Science and Technology* 16(11): 7197-7206.
- Karkush, M.O. and Yassin, S.2020.** Using sustainable material in improvement the geotechnical properties of soft clayey soil. *Journal of Engineering Science and Technology* 15(4): 2208-2222.
- Karkush, M.O., Ali, H.A. and Ahmed, B.A. 2018.** Improvement of Unconfined Compressive Strength of Soft Clay by Grouting Gel and Silica Fume. In *Proceedings of China-Europe Conference on Geotechnical Engineering* (pp. 546-550). Springer, Cham.
- Kavak, A. and Akyarli, A. 2007.** A Field Application for Lime Stabilization. *Env Geol* 51: 987–997.
- Khattab, S. I. and Khalaf, M. M. 2011.** Effect of Combined Stabilization by Lime and Cement on Hydraulic Properties of Clayey Soil Selected From Mosul Area. *Al-Rafidain Engineering* 20 (6):139-153.
- Manasseh, J. and Olufemi, A. I. 2008.** Effect of Lime on some Geotechnical Properties of Igumale Shale. *Electron J Geotech Eng* 13:1–12.
- Marques, M. E., Leroueil, S., and Almeida, M. S. 2004.** Viscous Behaviour of St Roch-de-l’Achigan Clay, Can. *Geotech. J.* 41: 25-38.
- Mohammed, A. A. and Alsharief, A. M. 2015.** Engineering Properties of Lime Stabilized Swelling Soils from Sudan. *International Journal of Science, Engineering and Technology Research (IJSETR)* 4 (10): 3595-3600.
- Noolu, V., & Pillai, R. J. 2018.** Multi-scale laboratory investigation on black cotton soils stabilized with calcium carbide residue and fly ash. *Journal of Engineering Research* 6(4): 1-15.
- Osinubi, K. J. and Nwaiwu, M. O. 2006.** Compaction Delay Effects on Properties of Lime-Treated Soil. *J Mater Civil Engineering* 18 (2):250–258.

Qi, J., Ma, W., and Song, C. 2008. Influence of Freeze–Thaw on Engineering Properties of a silty soil. *Cold Regions Science and Technology* 53 (3):397–404.

Rao, S. M. and Shivananda, P. 2005. Compressibility Behaviour of Lime-Stabilized Clay. *Geotechnical and Geological Engineering* 23: 309–319.

Rashed, K. A., Salih, N. B., and Abdalla, T. A. 2017. Correlation of Consistency and Compressibility Properties of Soils in Sulaimani City. *Sulaimani Journal for Engineering Sciences* 4 (5): 87-95.

Tang, A. M., Cui, Y. J., and Barnel, N. 2007. A New Isotropic Cell for Studying the Thermo-Mechanical Behavior of Unsaturated Expansive Clays. *Geotechnical Testing Journal* 30: 341-348.

Tsutsumia A.,n , Tanaka H. 2012. Combined effects of strain rate and temperature on consolidation behavior of clayey soils. *Soils and Foundations* 52(2): 207-2015

Villar, M. V., Gómez-Espina, R., and Lloret, A. 2010. Experimental Investigation into Temperature Effect on Hydro-Mechanical Behaviours of Bentonite. *Journal of Rock Mechanics and Geotechnical Engineering* 2: 171-78.

Zhao, H., Liu, J., Guo, J., Zhao, C., and Gong, B. 2014. Reexamination of Lime Stabilization Mechanisms of Expansive Clay. *J Mater Civil Engineering* 7. doi:10.1061/(ASCE)MT.1943-5533.0001040.